

## **brix-E-SL1** (3 - Pack )

1.0 mm



**brix-E-SL1 is a pigmented, solvent-free, easily applied self-smoothing epoxy floor coating system, designed to protect concrete substrates.**

brix-E-SL1 is typically applied in one layer for a smooth finish, however can be broadcast with graded quartz aggregate while wet and sealed to provide a slip-resistant textured finish.

brix-E-SL1 provides an impervious, easy-to-clean, hygienic and seamless surface with excellent wear and chemical resistance as well as high mechanical strength. brix-E-SL1 is designed for use in aggressive industrial areas subject to frequent foot traffic.

### **Specific Gravity**


1.65 g/cm<sup>3</sup>@ 25°C

### **Working Time**

~20 – 25 minutes @ 25°C (usable working life of material following mixing and immediate spreading as per the application instructions).

### **Coverage**

The recommended coverage of brix-E-SL1 is 1.65 kg/m<sup>2</sup> at 1 mm. A double priming of brix-E-Prime is recommended.

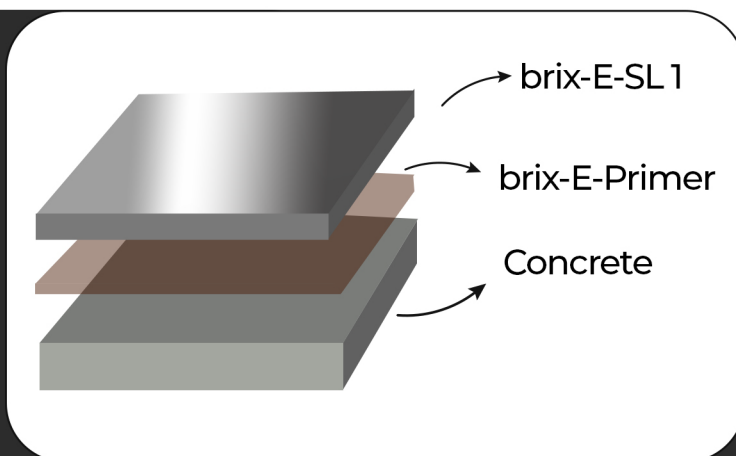

### **Thermal Resistance**

Tolerant up to 60°C

### **Abrasion Resistance**

Taber Abrader: 90 mg Loss per 1000 cycles

### **Compressive Strength**

>50 N/mm<sup>2</sup>

### **Flexural Strength**

>30 N/mm<sup>2</sup>

### **Bond Strength**

>1.5 MPa

### **Speed of Cure**

Light Foot Traffic – 18 hours  
Light Wheeled Traffic – 24 hours  
Heavy Duty Traffic – 72 hours  
Full Chemical Cure – 7 days

### **Storage**

All components should be stored off the ground, in a cool dry area, away from direct sunlight between 10 – 30°C

# **brix-E-SL1 (3 - Pack )**

1.0 mm



## **Application Temperature Range**

~10 – 30°C is recommended. Outside of this range, heating or cooling equipment should be used to achieve ambient conditions. The substrate, before priming, should be at least 3°C above the dew point to reduce the risk of condensation or blooming. This should be maintained for 48 hours after application.

## **Substrate Requirements**

brix-E-SL1 is suitable for application on cementitious substrates and suitable polymer modified screeds.

All substrates should be capable of bearing loads, free of cracks and voids as well as free from laitance, dust and other contamination including dirt, oil, grease, coatings, and surface treatments. The substrate should be sound with a minimum compressive strength of 25 N/mm<sup>2</sup> and a minimum tensile strength (pull-off) of 1.5 N/mm<sup>2</sup>. The concrete substrate must be a minimum of 28 days old and the residual moisture content must be a maximum of 4% CM.

Where the concrete substrate is in contact with the ground, an effective damp proof membrane should have been incorporated into the slab design.

## **Substrate Preparation**

Substrates should be mechanically prepared using captive vacuum enclosed shot blasting or diamond grinding, to remove surface cement based laitance and previous surface treatments leaving an open textured mechanically prepared surface.

Weak concrete / polymer modified screed must be removed and repaired using recommended products. Imperfections in the concrete (holes and cracks) should be filled using epoxy patching compound.

## **Application Instructions**

### **Priming**

If the slab requires priming, brix-E-Prime is recommended. See brix-E-Prime data sheet for more details. Allow to cure before applying the brix-E-SL1. To improve inter-coat adhesion, broadcast Natural Quartz (0.2 – 0.5 mm) while the primer is still wet. For details of other specialist primers contact our Technical Department.

### **Mixing**

The contents of the brix-E-SL1 (Part A) should be mixed for approximately 2 – 3 minutes. The contents of brix-E-SL1 (Part B) should be drained into the brix-E-SL1 (Part A) component and the two materials thoroughly mixed at speed of 350 rpm for two minutes.

## **brix-E-SL1** (3 - Pack ) 1.0 mm



The mixed liquid should then be poured into a clean suitably sized separate mixing container and mixed for a further 1 – 2 minutes. Add the contents of the Filler C to the mixed resin and mix for a further three minutes or until homogenous.

### **Application**

brix-E-SL1 should be poured onto the surface and spread over the entire area using a serrated spatula or notched trowel at a rate of 1.80 kg/m<sup>2</sup> per mm thickness before being back-rolled with a spike roller to a self-smoothing gloss finish.

Broadcast with Natural Quartz (0.7 – 1.2 mm) while the brix-E-SL1 coating is still wet if seeking a slip-resistant textured finish. Once cured, seal the anti-slip profile with one to two coats of brix-E (Universal)

### **Overcoating**

Overcoating should be carried out within 24 hours of application. If longer than 24 hours it will be necessary to lightly grind the surface by mechanical means before overcoating is carried out.

### **Further Information**

Information relating to the safe handling of this product can be found in the Material Safety Data Sheet. Local regulations concerning the safe handling of resin based coating materials must be observed. Suitable protective clothing including suitable eye protection must be worn at all times.

All consumptions listed are for recommendation purposes only. Detailed application instructions and system build-up advice can be provided on request through our Technical Services team.

Products are guaranteed against defective material and manufacture and are sold subject to its standard Terms and Conditions of Sale, copies of which can be obtained on request



[www.ghanatiprojectsltd.com](http://www.ghanatiprojectsltd.com)



+91 (44) 247 4 8849



[info@ghanatiprojectsltd.com](mailto:info@ghanatiprojectsltd.com)